



Welding of Martensitic Creep-Resistant Steels

The relationship between preheat and M_s temperatures was investigated

BY L. BÉRES, A. BALOGH AND W. IRMER

ABSTRACT. The majority of equipment and pipelines working at high temperatures in fossil-fueled power stations are made of creep-resistant steel with 9 to 12% chromium. For joining this type of steel, martensitic welding is undertaken, which is carried out following preheating to a temperature lower than the M_s . The preheat temperature is usually determined by experiments or following normal industrial practice. In spite of this, some materials are markedly crack sensitive, and moreover, cracks form in the welded joints. The authors have carried out detailed investigations to explore the reason for this phenomenon and have constructed a method to reduce such failures. The principal goal of this research was to provide a solution for welding of high-chromium, martensitic, creep-resistant steel with repeatable high quality.

Introduction

The characteristic types of martensitic creep-resistant steels are 0.2C 12Cr 1Mo and the recently developed 0.1C 9Cr 1Mo. The conventional continuous cooling transformation (CCT) diagrams belonging to a given chemical composition are presented in Figs. 1 and 2 (Refs. 1, 2). Notably, there is an 80°C difference in the M_s temperature of the two steel grades. The difference is due to the lower carbon (0.1%) and lower chromium (3%) content of the 9Cr steel, since the other alloying elements are the same. This observation confirms the common knowledge that the composition of the steel affects the M_s temperature.

Welding practice, temperature mea-

surements and calculations equally show that in spite of the widely used preheat temperature of 300°C and a correspondingly high heat input, the metal austenitized during welding cools to 500°C within 100 to 150 seconds and, as a result, the cooling curves are far removed from the austenite transformation curves. This suggests that the previously austenitized volume reaches the M_s temperature in a fully austenitic condition, and subsequently cools further to the preheat temperature with some part of the austenite therefore transforming into martensite. At low temperature (below M_p), following the welding operation, the retained austenite transforms into martensite independently of the preheat temperature and the duration of welding.

In the weld metal and part of the heat-affected zone (HAZ), where the transformation occurred, the proportion of martensite is always considerable; therefore, during welding, a certain risk of cracking may need to be considered. As a consequence of these arguments, welding engineers may need to have a general knowledge of the most important microstructural transformations and the related changes in strength (Ref. 3).

Characteristic Changes in the Microstructure of Creep-Resistant Steels

The quantity of martensite transformed from austenite depends on the temperature undercooling below the M_s (Ref. 4). This transformation is almost independent of the composition, and takes place in all steel grades as shown in Fig. 3.

Initially, this relationship has a linear characteristic, and it is suggested this may be estimated by a straight line by which the transformation is completed at $M_s - 126^\circ\text{C}$. Where the volume fraction of martensite is above 90%, the transformation slows down and finishes at approximately $M_f = (M_s - 190) \pm 10^\circ\text{C}$.

Ornig (Ref. 5) considered the section of the Schaeffler diagram under 18% chrome-equivalent was not accurate. Considering the detail in Fig. 3, it is possible to derive a regression equation suitable for estimation of the M_s temperature for any steel grade with very good fit (Refs. 6, 7). This was made possible by the authors' research, which is the subject of this paper. The basis of our analysis is supported by the latest results of Ref. 8.

The suggested equation for the M_s temperature of martensitic creep-resistant steels is as follows (concentrations are in wt-%):

$$M_s = 454 - 210 C + \frac{4.2}{C} - 27 \text{ Ni} - 7.8 \text{ Mn} - 9.5 (\text{Cr} + \text{Mo} + \text{V} + \text{W} + 1.5 \text{ Si}) - 21 \text{ Cu} \quad (1)$$

The good fit for this equation is characterized by the fact the difference between the calculated and the measured temperatures is only a few degrees and the correlation coefficient is very close to 1 (0.9898).

KEY WORDS

Martensitic Steel
Chrome-Moly
Weld Cracking
Creep Resistant
High Temperature
Power Plants

L. BÉRES and A. BALOGH are Associate Professors, University of Miskolc, Hungary. W. IRMER is Professor, University of Magdeburg, Germany.

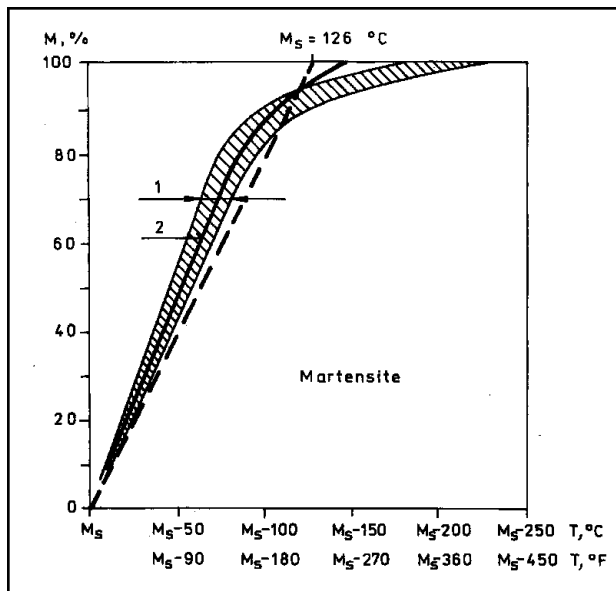


Fig. 3 — The fraction of martensite in the microstructure against the temperature below M_s (Ref. 4). 1 — Steven and Haynes (Carbon steel, $C = 0.35\%$); 2 — Kauhausen (alloy steel, 0.2C 12Cr 1Mo).

Properties of Previously Austenitized Steels Cooled to Preheat Temperature

On the basis of the previous paragraph, it may be concluded that neither a high preheat temperature is favorable (because of the crack sensitivity during cooling), nor one that is too low (because of the risk of cracking during welding due to excessive martensite formation).

Investigations were conducted to determine the minimum temperature necessary, *i.e.*, the optimum preheat temperature. For this purpose, tensile specimens previously austenitized then cooled to the testing temperature were examined. In the tested condition, the microstructure was found to be the same as in the HAZ of the welded joint after transformation occurred due to the welding heat cycle.

In the course of research on the 0.2C-12Cr-1Mo and 0.1C-9Cr-1Mo type steels, the chemical compositions given in rows 6 and 7 of Table 1 were used. Five-mm-diameter, cylindrical specimens were austenitized at 1050°C for 10 min. Then the specimens were cooled to the tensile testing temperature within 30 seconds and placed in the furnace of a computer-controlled, MTS-type testing machine, where they were test loaded in the warm condition by a tensile force until fracture. Considering the CCT diagrams of these steel heats presented in Figs. 1 and 2, the reader may observe this rapid cooling guarantees a fully austenitic microstructure when the temperature decreases to the M_s temperature and the austenitic-

martensitic condition at the testing temperature.

The results of these tensile tests are given in Table 2. It can be seen from this data that the specific elongation of both steel heats decreases sharply while their strength increases markedly. These phenomena are the result of the increasing martensite content, the quantity of which can be estimated using Fig. 3, after calculation of the M_s temperature by Equation 1.

According to the data in Table 2, the elongation only decreases significantly below the M_s temperature (Ref. 10). Above the M_s temperature, it appears to be relatively constant.

The temperature at which the steel is tough enough to suffer the strain originated from welding can be selected only with mutual consideration of ultimate tensile strength, specific elongation and martensite content. To assist understanding of this concept, the three curves in the function of the temperature below the M_s are illustrated in one graph.

Figure 4 illustrates the properties of the steel whose composition is given in row 6 of Table 1. Since the composition of the 0.2C-12Cr-1Mo-type creep-resistant steel varies across a broad range, the

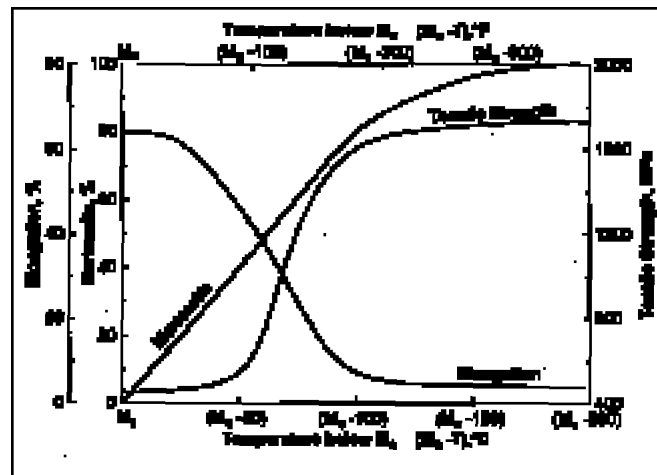


Fig. 4 — Martensite fraction, elongation, and tensile strength of a 0.2C-12Cr-1Mo-type creep-resistant steel cooled from the austenitizing temperature to the testing temperature.

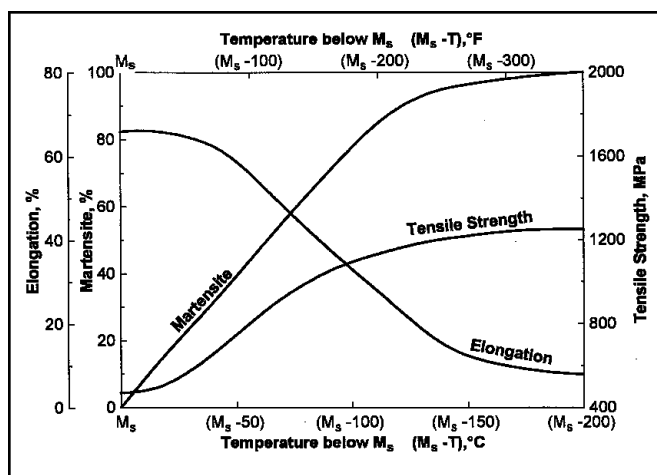


Fig. 5 — Martensite fraction, elongation and tensile strength of a 0.1C-9Cr-1Mo-type creep-resistant steel cooled from the austenitizing temperature to the testing temperature.

M_s temperature changes between 254 and 324°C, depending on the composition. Figure 4 seems to be suitable to characterize all the steel heats within the standard interval, particularly because the composition of the experimental heat is close to the mean of the standard range.

In case of steels with 0.2% C, there is a generally accepted welding rule for avoiding crack formation that the maximum tensile strength in the joint should not exceed 1000 MPa (approximately 300–350 HV). Figure 4, illustrating the properties of the steel valid for conditions of welding, assists in selecting the correct preheat temperature. To keep tensile strength below 1000 MPa, the preheat temperature must be high enough such that a minimum 30 to 35% of martensite should be formed. On the basis of this

